

Phononic self-energy effects and superconductivity in CaC₆A. Sanna,^{1,2} S. Pittalis,³ J. K. Dewhurst,^{1,2} M. Monni,⁴ S. Sharma,^{1,2} G. Umbarino,⁵ S. Massidda,⁴ and E. K. U. Gross^{1,2}¹*Max-Planck-Institut für Mikrostrukturphysik, Weinberg 2, D-06120 Halle, Germany*²*European Theoretical Spectroscopy Facility (ETSF)*³*Department of Physics and Astronomy, University of Missouri–Columbia, Columbia, Missouri 65211, USA*⁴*Dipartimento di Scienze Fisiche, Università degli Studi di Cagliari, Cagliari, Italy*⁵*C.N.I.S.M. Dipartimento di Fisica Politecnico di Torino, C.so Duca degli Abruzzi 24, 10129 Torino, Italy*

(Received 13 August 2011; revised manuscript received 12 February 2012; published 14 May 2012)

We study the graphite intercalated compound CaC₆ by means of Eliashberg theory. We perform an analysis of the electron-phonon coupling and define a minimal six-band anisotropic structure, which leads to a Fermi-surface dependence of the superconducting gap. A comparison of the superconducting gap structure obtained using the Eliashberg and the superconducting density functional theory is performed. We further report the anisotropic properties of the electronic spectral function, the polaronic quasiparticle branches, and their interplay with Bogoljubov excitations.

DOI: [10.1103/PhysRevB.85.184514](https://doi.org/10.1103/PhysRevB.85.184514)

PACS number(s): 74.70.Wz, 71.38.–k, 74.25.Jb, 74.25.Kc

I. INTRODUCTION

The electron-phonon interaction leads to many significant physical phenomena in solids (notably, superconductivity), and has therefore been studied extensively both in model systems and in real materials. One important aspect of this kind of interaction is the formation of a coupled electron-phonon system with new interesting features such as the appearance of polaronic subbands branching from the main electronic bands. These low-energy features of the electronic structure can be observed thanks to the recent developments in the resolution of angle-resolved photoemission spectroscopy (ARPES).

The theoretical background to deal with metallic polarons has been laid down by Engelsberg and Schrieffer (ES).¹ For this, they used a field-theoretical approach combined with Einstein-Debye model to mimic the phonon spectrum. The ES theory shows the damping of electrons by phonons and the development of branches in the electronic dispersion corresponding to energy and strength of the phonon modes. In superconductors, the electron-phonon interaction leads to the formation of a superconducting gap below the critical temperature T_c . These phenomena can be well described within the Eliashberg theory, which extends the ES theory to the superconducting state^{2,3} and reduces to the ES theory in the nonsuperconducting normal state.

Due to several computational complexities, a proper account of the material specific electronic and phononic structures could not be achieved until very recently: Eiguren *et al.*⁴ and Eiguren and Ambrosch-Draxl⁵ studied the effect of the electron-phonon interaction on the electronic self-energy in the normal state. The main properties of the spectral function in the superconducting state have been reported by Scalapino^{3,6} and, more recently, have also been studied using the ARPES experimental data.^{7–9} However, to the best of our knowledge, no first-principles attempt has been made to study the effect of polarons in the superconducting state.

In this work, we use the Eliashberg^{2,3,10,11} method to study the behavior of ES polarons; a detailed analysis of the electronic self-energy, including electron-phonon contributions is performed. In particular, the features originating from the anisotropy of the electron-phonon coupling are investigated.

Most importantly, it is shown how the polaronic branches change in the superconducting state.

The system that is considered for this analysis is the graphite intercalated compound CaC₆. This material has the highest superconducting T_c observed so far (11.5 K) among the group of graphitic compounds. Graphite-related materials have attracted considerable interest in the last few years, mostly due to the appealing possibility of tuning their physical properties.¹² In particular, it is possible to vary the conductivity of graphite from semimetallic¹³ to metallic and to superconducting^{14–22} by adjusting the level of intercalation. In Ca intercalated graphite, superconductivity arises from the strong electron-phonon coupling provided both by C and Ca phonon modes.^{18,23} This coupling is strongly anisotropic with C- and Ca-related phonons acting selectively on the multiple Fermi-surface (FS) sheets of the system.²⁴ These peculiarities make the system particularly interesting.

The paper is organized as follows: In Sec. II, the main concepts and physical quantities describing our results are introduced by reviewing the Eliashberg theory of superconductivity. Section III is devoted to a detailed description of the principal computational techniques employed in this work. In Sec. IV, results for CaC₆ are discussed. Section IV A reports on the structure of the electron-phonon interaction. Section IV B focuses on the numerical solutions of the Eliashberg equations with a μ^* determined using results from density functional theory for superconductors (SCDFT) calculations. In Sec. IV C, the polaronic features of the excitation spectrum of CaC₆ are elucidated, both in the normal state (Sec. IV C 1) and in the superconducting state (Sec. IV C 2). Finally, conclusions are drawn in Sec. V.

II. METHODS

The central quantity in the Nambu-Gor'kov formalism of superconductivity is the 2×2 Green's function¹¹

$$\bar{G}(\mathbf{k}, i\omega_n) \equiv \begin{pmatrix} G(\mathbf{k}, i\omega_n) & -F(\mathbf{k}, i\omega_n) \\ -F^*(\mathbf{k}, i\omega_n) & -G(-\mathbf{k}, -i\omega_n) \end{pmatrix}, \quad (1)$$

where $G(\mathbf{k}, i\omega_n)$ and $F(\mathbf{k}, i\omega_n)$ are, respectively, the normal and anomalous electronic Green's functions in reciprocal space. ω_n are the fermionic Matsubara frequencies given by $\omega_n = \pi(2n+1)k_B T$ with T being the temperature and k_B the Boltzmann constant. Following a well-established procedure,¹⁰ the noninteracting Kohn-Sham system with Green's function $\tilde{G}_0(\mathbf{k}, i\omega_n) = [i\omega_n\sigma_0 - \xi_{\mathbf{k}}\sigma_3]^{-1}$ is used as a starting point. Here, σ_j ($j = 0 \dots 3$) are the Pauli matrices and $\xi_{\mathbf{k}}$ are the Kohn-Sham eigenvalues relative to the Fermi energy. The interacting Green's function can then be obtained using perturbation theory:

$$[\tilde{G}(\mathbf{k}, i\omega_n)]^{-1} = [\tilde{G}_0(\mathbf{k}, i\omega_n)]^{-1} - \tilde{\Sigma}(\mathbf{k}, i\omega_n). \quad (2)$$

The following approximation for the electronic self-energy is used:

$$\begin{aligned} \tilde{\Sigma}(\mathbf{k}, i\omega_n) = & -k_B T \sum_{\mathbf{k}', n'} \sigma_3 \tilde{G}(\mathbf{k}', i\omega_{n'}) \sigma_3 \\ & \times \left[\sum_{\nu} |g_{\mathbf{k}, \mathbf{k}', \nu}|^2 D_{\nu}(\mathbf{k} - \mathbf{k}', i\omega_n - i\omega_{n'}) \right. \\ & \left. + \sigma_1 W(\mathbf{k} - \mathbf{k}') \right], \quad (3) \end{aligned}$$

where D is the phonon propagator [$D = -2\omega_{\mathbf{q}, \nu} / (\omega_n^2 + \omega_{\mathbf{q}, \nu}^2)$], $g_{\mathbf{k}, \mathbf{k}', \nu}$ are the electron-phonon matrix elements²⁵ between states with wave vectors \mathbf{k} and \mathbf{k}' due to a phonon mode of index ν and wave vector $\mathbf{q} = \mathbf{k} - \mathbf{k}'$, and $\omega_{\mathbf{q}, \nu}$ is the frequency of the mode obtained via linear response²⁵ of the Kohn-Sham system. This way of calculating $\omega_{\mathbf{q}, \nu}$ is known to lead to a very good agreement with the measured phononic branches, at least for standard metals and insulators.²⁵ W in Eq. (3) is the screened static electron-electron interaction: it accounts for those parts of the interaction which do not involve any phononic contribution. The σ_1 factor in front of W accounts for the fact that exchange and correlation effects are already included in $\tilde{G}_0(\mathbf{k}, i\omega_n)$.²⁶ Then, only off-diagonal contributions of W are retained in $\tilde{\Sigma}$.

The treatment of the Coulomb term needs particular care. Within Eliashberg theory, an arbitrary cutoff in \mathbf{k} space is needed in order to avoid serious convergence problems in the Matsubara summation.^{3,27} A conventional way to deal with this problem is to choose an energy cutoff of the order of the Fermi energy, and to assume that the product of W with the density of states (DOS) is constant: $\mu = WN$, N being the DOS per spin at the Fermi energy. It is then possible to restrict the Matsubara integration to low energies (a fraction of eV) by a renormalization procedure $\mu \rightarrow \mu^*$ introduced by Morel and Anderson.^{3,27,28} μ^* can be calculated within the random phase approximation^{24,29,30} (RPA) and the resulting T_c are usually in reasonable agreement with experiments.^{10,31} However, usually μ^* is adjusted to obtain the experimental T_c .

The self-energy in Eq. (3) is \mathbf{k} dependent and leads to anisotropic Eliashberg equations, which are computationally very demanding. A simplification can be introduced, retaining a minimal anisotropic structure needed for the properties of interest. The FS may be divided into portions (FS sheets), with each sheet identifying a corresponding intersecting energy band. These FS sheets and energy bands can be labeled using the same index (say, J). We shall refer to such a division as to

a *multiband* decomposition (details of our procedure are given in Sec. IV A).

The electron-phonon coupling can be averaged over prescribed multiband divisions [see Eqs. (10) and (11)]. Corresponding multiband resolved self-energy, Σ_J , expanded in the basis of Pauli matrices has a form

$$\Sigma_J(n) = i\omega_n[1 - Z_J(n)]\sigma_0 + \Delta_J(n)Z_J(n)\sigma_1 \quad (4)$$

(terms which only result in a rigid shift of the Fermi level are neglected). The multiband resolved Green's function reads as

$$\tilde{G}_J(\mathbf{k}, i\omega_n) = \frac{-\begin{pmatrix} i\omega_n Z_J(n) + \xi_{J\mathbf{k}} & \Delta_J(n)Z_J(n) \\ \Delta_J(n)Z_J(n) & i\omega_n Z_J(n) - \xi_{J\mathbf{k}} \end{pmatrix}}{[Z_J(n)\omega_n]^2 + \xi_{J\mathbf{k}}^2 + [\Delta_J(n)Z_J(n)]^2}, \quad (5)$$

where $\xi_{J\mathbf{k}}$ are the Kohn-Sham eigenvalues in the J th band. Using Eqs. (4) and (5) in the Dyson equation, we arrive at the following set of coupled self-consistent equations:^{2,3,10,31}

$$Z_J(n) = 1 + \frac{\pi k_B T}{i\omega_n} \sum_{m, J'} \lambda_{JJ'}(n, m) \frac{i\omega_m Z_{J'}(m)}{R_{J'}(m)}, \quad (6)$$

$$\Delta_J^{ph}(n) = \pi k_B T \sum_{m, J'} \lambda_{JJ'}(n, m) \frac{\Delta_{J'}(m)Z_{J'}(m)}{R_{J'}(m)}, \quad (7)$$

$$\Delta_J^C(n) = -\pi k_B T \sum_{m, J'} \mu_{JJ'}^* \frac{\Delta_{J'}(m)Z_{J'}(m)}{R_{J'}(m)}, \quad (8)$$

$$R_J(n) = \sqrt{(\omega_n^2 + \Delta_J^2(n))Z_J^2(n)}, \quad (9)$$

$$\lambda_{JJ'}(n, m) = \int d\omega \frac{2\omega\alpha^2 F_{JJ'}(\omega)}{(\omega_n - \omega_m)^2 + \omega^2}. \quad (10)$$

Here, $\Delta_J(n) = \Delta_J^{ph}(n) + \Delta_J^C(n)$ is the total superconducting gap accounting for phononic and Coulombic contributions on the J th FS sheet at frequency $i\omega_n$. $Z_J(n)$ is the (phononic) mass renormalization function. This term enters in the diagonal part of the electronic self-energy and contributes both to the superconducting state and the normal state. Due to the assumption that all the diagonal contributions stemming from W are already accounted at the level of the normal state Kohn-Sham system, $Z_J(n)$ has a purely phononic character.

The off-diagonal Coulombic contributions are accounted by the FS-dependent $\mu_{JJ'}^*$. In this work, we choose $\mu_{JJ'}^*$ in such a way to reproduce the gap structure obtained within SCDF (Refs. 24 and 30) (we shall come back to this point in Sec. IV B). Since $\Delta^{ph}(n)$ goes to zero for frequencies much larger than the phononic scale, the cutoff in the Matsubara frequency introduced for Coulombic terms³ can be uniformly applied to all the terms of the Eliashberg equations.

$\alpha^2 F_{JJ'}(\omega)$ in Eq. (10) is the band-resolved Eliashberg function. This quantity results from the averaging of the electron-phonon interaction over FS sheets:

$$\alpha^2 F_{JJ'}(\omega) = \frac{1}{N_J} \sum_{\substack{\mathbf{k} \in J \\ \mathbf{k}' \in J' \\ \nu}} \delta(\xi_{\mathbf{k}})\delta(\xi_{\mathbf{k}'})\delta(\omega - \omega_{\mathbf{q}, \nu}) |g_{\mathbf{k}, \mathbf{k}'}^{\nu}|^2, \quad (11)$$

where N_J is the density of states per spin at the J th FS portion.

Once the gap function $\Delta_J(n)$ and the mass renormalization function $Z_J(n)$ have been obtained on the imaginary axis solving the Eliashberg equations [Eqs. (6)–(10)], they can be efficiently continued to the real axis via the Padé approximant

technique,^{32–34} allowing the computation of the real-axis retarded Green's function. In particular, we will deal with $G := \bar{G}^{11}$, which is given by

$$G_J(\mathbf{k}, \omega) = \frac{\omega Z_J(\omega) + \xi_{J\mathbf{k}}}{[\omega Z_J(\omega)]^2 - \xi_{J\mathbf{k}}^2 - [\Delta_J(\omega) Z_J(\omega)]^2}, \quad (12)$$

with the corresponding spectral function defined as

$$A_J(\mathbf{k}, \omega) = -\frac{1}{\pi} \text{Im} G_J(\mathbf{k}, \omega). \quad (13)$$

The energy and lifetime of a quasiparticle are given by the real part and (the absolute value of the) imaginary part of the pole positions, respectively. The spectral function may have broader structures and, thus, the concept of quasiparticle may not apply rigorously. In order to extract the main features, we look for the zero z_p of the denominator of G , i.e., we look for solutions of the equation

$$z_p = \frac{\sqrt{\xi_{J\mathbf{k}}^2 + [\Delta_J(z_p) Z_J(z_p)]^2}}{Z_J(z_p)} \quad (14)$$

in the complex plane.

III. COMPUTATIONAL DETAILS

Electronic eigenvalues, phononic frequencies, and electron-phonon matrix elements are calculated using the ESPRESSO pseudopotential based package.^{35,36} All calculations are done using the GGA (generalized-gradient approximation) with the Perdew-Wang³⁷ parametrization for the exchange-correlation functional. Ultrasoft pseudopotentials³⁸ are employed. A 30-Ry cutoff is fixed for the plane-wave expansion of the wave functions and 300 Ry for the electronic charge. The Brillouin zone is sampled with a $6 \times 6 \times 6$ \mathbf{k} -point grid, and electron-phonon matrix elements are obtained on a $10 \times 10 \times 10$ grid. More details can be found in Ref. 24.

The double Brillouin zone integration appearing in the definition of the band-resolved Eliashberg functions in Eq. (11) is evaluated with a Metropolis integration scheme. Random \mathbf{k} points are generated on the Brillouin zone, then each \mathbf{k} point is accepted or rejected with a probability depending on $\xi_{\mathbf{k}}$, and its weight is set inversely proportional to the acceptance probability. We use a set of about 2×10^4 accepted \mathbf{k} points per band. Then, electron-phonon matrix elements on this random mesh are obtained via interpolation from those calculated on the regular grid.

Eliashberg equations are solved using a 2500-meV cutoff of the Matsubara frequencies, with the cutoff for the Coulombic interaction equal to 500 meV. Both parameters are much larger than the maximum phonon frequency of CaC_6 , which is about 200 meV. The number of Matsubara frequencies at each temperature is fixed by the energy cutoffs, and the M Matsubara frequencies on the positive imaginary axis are used to construct (M, M) Padé approximants, which are used for the analytic continuations³⁹ to the real axis.

TABLE I. (Color online) Electron-phonon coupling $\lambda_{JJ'}$ and DOS for the three-band FS (top) and six-band FS (bottom) divisions. DOS is given in states/eV/spin. The first index runs over the columns. Isotropic DOS and λ are 0.787 and 0.870, respectively. The picture on the top represents the FS of CaC_6 : the external portion in green; the internal sphere in blue; and the hexagon that cuts the sphere in red. The labels “a” and “b” correspond to the additional splitting defining the six-band division.

	1	2	3							
1	0.301	0.136	0.257							
2	0.546	0.239	0.479							
3	0.427	0.198	0.367							
DOS	0.412	0.104	0.249							
	1a	1b	2a	2b	3a	3b				
1a	0.163	0.126	0.099	0.033	0.201	0.046				
1b	0.179	0.140	0.105	0.035	0.221	0.050				
2a	0.331	0.245	0.151	0.084	0.384	0.096				
2b	0.271	0.202	0.206	0.047	0.400	0.080				
3a	0.252	0.194	0.145	0.061	0.309	0.073				
3b	0.206	0.157	0.128	0.044	0.259	0.060				
DOS	0.250	0.176	0.075	0.031	0.200	0.056				

IV. RESULTS AND DISCUSSION

A. Properties of the electron-phonon coupling

We calculate the Eliashberg function defined by Eq. (11) in three different ways:

(i) Averaging the electron-phonon coupling over the full surface (referred to as one-band FS or isotropic approximation).

(ii) Splitting the FS into three parts: this is shown with three different colors in the FS (see Table I). The division of the Fermi surface leads to a division in the electronic bands shown in the band-structure plot of Fig. 5; an electronic band and a portion of the FS have the same color if they intersect. The first portion FS 1 is the external FS sheet (shown in green), which comes from π states. FS 2 (shown in blue) is the spherical Ca Fermi surface. FS 3 (shown in red) is the π prism, a two-dimensional FS having the shape of a hexagonal prism which crosses the spherical Ca Fermi surface (the corresponding electronic band is the band 3). This division is referred to as the three-band FS approximation.

(iii) Splitting the FS into six parts: each of the three portions in the three-band FS approximation is further split into two parts. The above π (external) FS has been divided into a less coupled²⁴ outer part with $|\mathbf{k}_{xy}| > 0.4$ a.u., and the rest; these two portions are referred to as 1a and 1b portions, respectively. The Ca spherical Fermi surface is cut into the 2a portion (with $|\mathbf{k}_z| < 0.18$ a.u.) and the 2b portion (the rest). The 3a and 3b portions for the π prism are defined in a similar manner. The same boundaries are used to further split the corresponding energy bands. This overall division is called the six-band FS approximation.

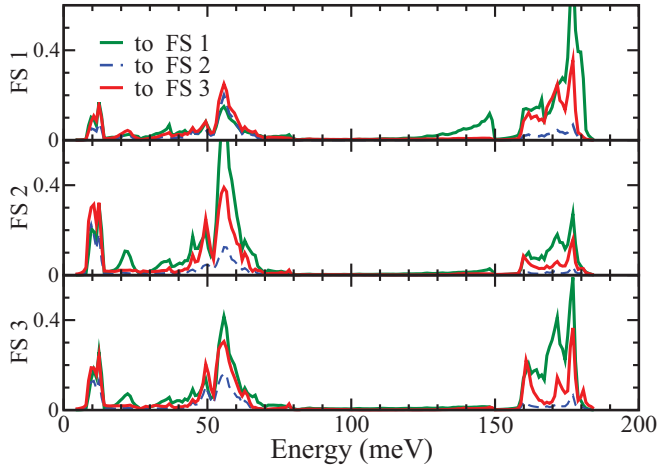


FIG. 1. (Color online) Three-band FS resolved $\alpha^2 F_{JJ'}(\omega)$ of CaC_6 . The three panels refer to the incoming FS, from which the electron is scattered, while the three lines in each panel refer to the outgoing FS.

In Table I is presented the DOS at the Fermi level, the intraband and the interband electron-phonon couplings

$$\lambda_{JJ'} = 2 \int \frac{\alpha^2 F_{JJ'}(\omega)}{\omega} d\omega. \quad (15)$$

In the three-band FS approximation, the interaction is dominated by the off-diagonal coupling terms, especially by the interband scattering from states on the spherical Ca Fermi surface to states on the π bands. The main reason for this is a strong electron-phonon coupling in the former (from 2 to 1) and large DOS in the latter (from 2 to 3). The full three-band $\alpha^2 F_{JJ'}(\omega)$ matrix (see Fig. 1) shows the distribution of the coupling among the various phonon modes; band 2 couples strongly with Ca modes (giving a low-frequency peak around 10 meV), while band 1 couples mainly with the high-frequency stretching C modes (at 170 meV). Band 3 shows the most homogeneous coupling (its intraband spectral function looks similar in shape to the total Eliashberg function).

The further decomposition into the six-band FS approximation does not introduce qualitative differences with respect to the three-band decomposition but, as we shall show, it results in a better quantitative description of the anisotropy of the superconducting properties.

B. Solution of Eliashberg equations

The Eliashberg equations are solved in three different ways corresponding to three ways in which the Eliashberg function defined in Sec. IV. The solution to the Eliashberg equations leads to a strong anisotropy in the gap (see Fig. 2); the smallest gap corresponds to the external FS (FS 1), while the highest value of the gap is related to the 2a structure, which forms the central part of the Ca spherical Fermi surface. We note that at the phononic level, the anisotropic structure obtained here agrees very well with the one obtained within SCDFT in Ref. 24 (see panels (e) and (f) in Fig. 2). If the T_c is determined from this gap function, without including the Coulomb interaction, it is not strongly affected by the multiband character (i.e., the anisotropy of the gap function);

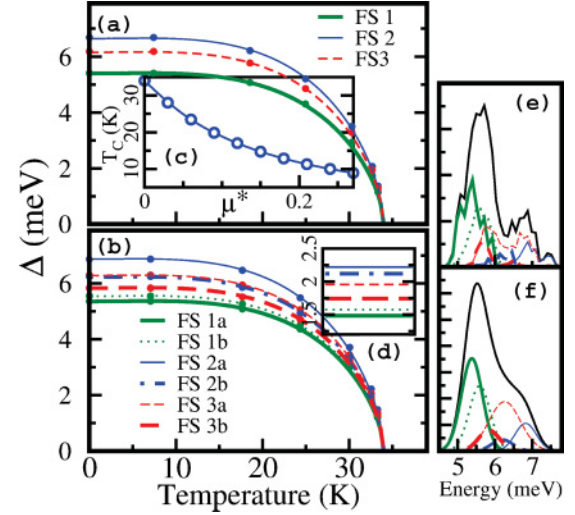


FIG. 2. (Color online) (a) Anisotropy of the superconducting gap in the three-band FS approximation and (b) six-band FS approximation. In (a), the dark green thick line is used for the gap computed over FS 1; the blue thin line for the gap computed over FS 2; and the red dashed line for gap computed over FS 3. In (b), dark green thick and dotted thin lines are used for 1a and 1b FS, respectively; blue thin and dash-dotted thick lines for 2a and 2b FS, respectively; and red dashed thick and dashed thin lines for 3a and 3b FS, respectively. (a) and (b) refer to phonon only calculations. Inset (c) shows the effect of the inclusion of the Coulombic interaction: the Eliashberg T_c is given as a function of μ^* (see text for details). Inset (d) reports the low-temperature multigap structure for $\mu^* = 0.21$. Panels (e) and (f) report the gap distribution functions (phonon only calculations) in the six-band FS approximation in SCDFT (Ref. 24) and Eliashberg theory (with a Gaussian broadening applied), respectively.

the isotropic T_c is about 33.5 K and only slightly higher in the six-band case with a value of 34 K.

In order to include the Coulomb interactions, the matrix $\mu_{JJ'}^*$ is needed. Typically, $\mu_{JJ'}^*$ is determined by fitting to the experimental data. However, for CaC_6 the SCDFT gap well reproduces the experimental measurements.^{40–44} Therefore, in this work, we determine $\mu_{JJ'}^*$ fitting to the gap structure obtained from SCDFT.

Interestingly, the simple *semi-isotropic* approximation $\mu_{JJ'}^* = \mu^* N_J / N$ turns out to be sufficient to reproduce the SCDFT gap. In the six-band FS approximation, the experimental $T_c = 11.5$ K is reproduced for $\mu^* \simeq 0.21$ [see inset (c) in Fig. 2]. With this choice of $\mu_{JJ'}^*$, the inclusion of Coulombic effects reduces the T_c without significantly affecting the anisotropic structure of the superconducting gap. The only difference is that, by including the Coulombic interaction, the gap corresponding to the 2b portion of the FS becomes slightly larger than the 3a portion [see Fig. 2(d)]. This choice of a semi-isotropic Coulombic pairing, which is often done in Eliashberg theory, can be validated by the present analysis. However, this can not be applied as a general rule; it has been shown, in cases such as in MgB_2 ,^{45,46} that a more detailed Coulombic structure is necessary to get the correct gap anisotropy.

Both $\Delta(n)$ and $Z(n)$ are purely real valued on the Matsubara frequencies. For the isotropic case, the frequency dependence of $\Delta(n)$ and $Z(n)$ is shown in Fig. 3(a). It is clear that $Z(n)$

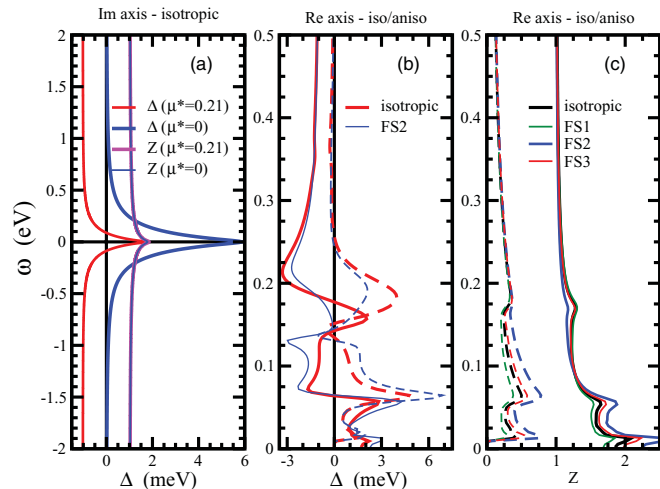


FIG. 3. (Color online) Eliashberg functions. (a) Superconducting gap and mass renormalization function calculated solving the isotropic Eliashberg equations on the imaginary axis. (b) Analytically continued gap function on the real axis. (c) Analytically continued mass renormalization function on the real axis. Full lines are used for the real part and dashed lines for the imaginary part of these complex functions. On the imaginary axis, the functions are purely real.

has a value of $1 + \lambda$ for small $|n|$ and then monotonically decreases to 1 at energies much larger than the available phonons. This behavior is almost independent of the values of μ^* and temperature. The $\Delta(n)$ function also monotonically decreases as a function of increasing energy. The low-energy value is the fundamental superconducting gap, while in the high-energy limit approaches $\Delta^C(n)$. For an isotropic and static Coulomb interaction, $\Delta^C(n)$ is both independent of \mathbf{k} and the Matsubara frequencies. More physical features emerge from the analytic continuation to the real axis. In particular, we see a three-peak structure in both the real and imaginary parts of $Z(n)$ that correlates with the peaks in the $\alpha^2 F_{JJ}(\omega)$.

C. Analysis of self-energy effects

1. Normal state: Isotropic approximation

We discuss in this section the simplest case in which the Eliashberg equations are solved above T_c . Since T_c is quite low with respect to the phonon energies, the solution above T_c is almost equivalent to imposing the solution at $\Delta = 0$ when $T = 0$. In this section, we use only the isotropic solutions of the Eliashberg equations and a parabolic band dispersion.

The solution of the Eliashberg equations gives $Z(\omega)$, which is shown in Fig. 3(c) (black line). Using $Z(\omega)$ as input, Eq. (14) is solved in order to obtain the quasiparticle dispersion curves reported in Fig. 4(a). This figure shows how the unperturbed electronic band, by getting dressed with the phononic self-energy, develops branches in correspondence with the three main phononic peaks in the Eliashberg function. These electronic quasiparticles dressed by the electron-phonon interaction, so-called polarons, are nearly dispersionless. Only one dispersive branch, which goes to zero from about 50 meV, is observed. This structure also has a very short lifetime (~ 100 meV). All the other polaronic modes have instead a longer lifetime (between 1 and 10 meV) and thus appear as

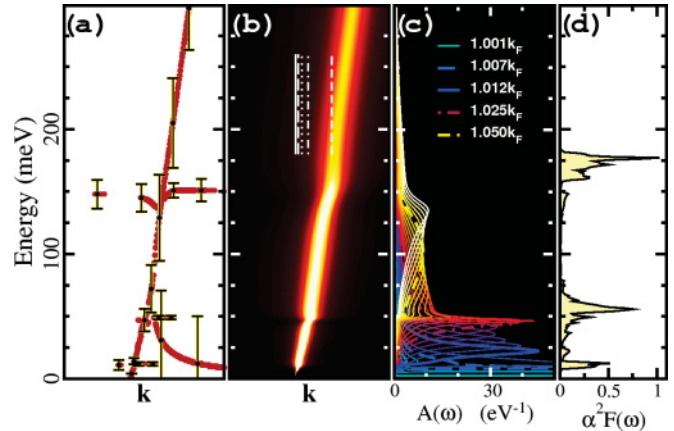


FIG. 4. (Color online) Polaronic bands and spectral function for the normal state in the isotropic approximation. On panel (a), the polaronic quasiparticle dispersion curves are shown. This is obtained from the real and imaginary parts of the solution of Eq. (14). The inverse lifetime of the state is given by $|\text{Im}(z_p)|$ and it is reported for some points as “error bar.” Panel (b) shows the spectral function $A(k, \omega)$. The abscissa represents the $|\mathbf{k}|$ axis, and the point in which $A(k, \omega)$ crosses is \mathbf{k}_F . In the ordinate, the frequency axis is reported. The color scale goes from zero to about 15 eV^{-1} [note that we cut it off to enhance the structures of $A(k, \omega)$]. Panel (c) shows $A(k, \omega)$ for different values of the momentum. A few values are highlighted and correspond to \mathbf{k} values indicated in panel (b). Panel (d) shows $\alpha^2 F(\omega)$ computed in the the isotropic one-band approximation.

sharp quasiparticles. However, the polaronic branches carry very little of the total spectral weight. Most of the spectral weight is still localized near the bare electron dispersion line. This can also be seen in Fig. 4(b), where the spectral function is shown in the same energy/momentum window as the quasiparticle plot. In this case, we see how the main electron band acquires a finite lifetime and instead of branchings only kinks appear. These kinks correspond to the three main peaks in the $\alpha^2 F(\omega)$.

To move from a qualitative description to a more quantitative one, the spectral function $A(\omega)$ is examined [see Fig. 4(c)]. At $\mathbf{k} = \mathbf{k}_F$, more than 50% of spectral weight is accounted for by a single peak of infinite lifetime at the Fermi energy. This peak [single green line in Fig. 4(c)] moves to higher energies with increasing \mathbf{k} vector (slowly growing in width) up to an energy of about 10 meV, where it merges with the polaronic branch generated by the low-frequency Ca modes (blue long-dashed line). Above 10 meV, the peak is broader (blue thick line) because the electrons can relax through the generation of Ca phonons. This broad peak then behaves in a similar way as the narrow peak below 10 meV; i.e., it increases in energy with \mathbf{k} up until it merges with another polaronic band which originates from the low-frequency C modes (red dotted-dashed line) and has an energy ~ 50 meV. It becomes very broad (yellow short-dashed line) and is difficult to follow as it merges with the high-frequency C mode. This behavior is very similar to the case of the Einstein phonons discussed by Engelsberg and Schrieffer in Ref. 1. In our case, this is due to the three-peak structure of the, $\alpha^2 F(\omega)$, i.e. due to the combined effect of the two dimensionality of graphite along

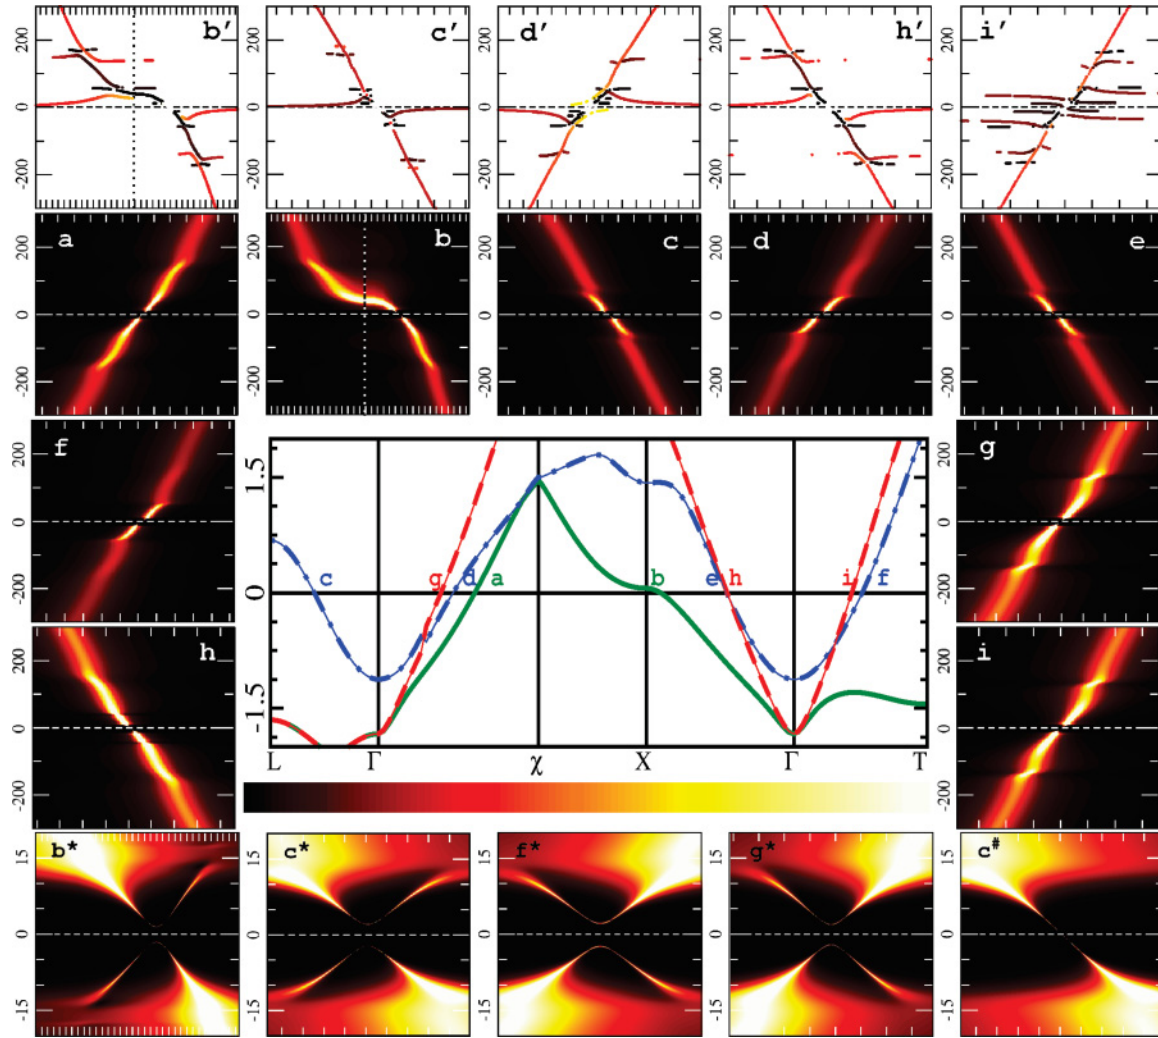


FIG. 5. (Color online) Polaronic bands and spectral function for the anisotropic and superconducting states of CaC_6 determined within the six-band approximation. The central panel shows the band structure of CaC_6 : the continuous green line is the $C\pi$ band corresponding to FS 1; the blue dotted-dashed line is the Ca interlayer band corresponding to FS 2; and the red dashed line is the second $C\pi$ band corresponding to FS 3 (see Table I for plots of the several FS portions). Further subdivisions are not reported explicitly. Panels (a) to (i) show the spectral function near the Fermi energy in a wide energy window of 300 meV. The letters correspond to the labeling of the crossing points in the central panel. The color scale goes from zero (black) to 15 eV^{-1} (white). Higher peaks in the spectral function have been cut off. Panels with a primed index show the quasiparticle spectrum (see text for details). These also show the polaronic branches together with the main electronic band. Colors are proportional to the linewidth of the quasiparticle state: black corresponds to zero and yellow/white correspond to about 0.1 eV . Panels (b*), (c*), (f*), and (h*), focusing on the superconducting gap (a logarithmic color scale is used), show a zoom of the spectral function near the Fermi energy in a narrow energy window of 20 meV. Panel (c[#]) is the same as (c*) but evaluated in the nonsuperconducting state.

with the presence of weakly bound Ca ions. Therefore, at the isotropic level, the self-energy effects in CaC_6 [type described by Eq. (3)] are particularly simple.

2. Normal and superconducting states: Anisotropic features

The degree of complexity of our analysis is increased by making use of the real KS band dispersions of CaC_6 .^{18,24} Multiple FSs that couple with different phonon branches are accounted for by adopting the six-band decomposition. As shown in Figs. 5(c)–5(f), the Ca band couples mostly with low-frequency modes, therefore it shows polaronic structures only up to 50 meV. One single kink can be observed in the

spectral function at 50 meV. The kink at 10 meV is not visible simply because below this frequency the spectral function itself is just a sharp peak.

The band that has the most structures is the one that produces the π -prism FS [Figs. 5(g)–5(i)] due to the coupling of all three sets of modes. The external FS, which couples mostly with high-frequency C modes, shows only a weak kink around 160 meV. The polaronic branchings [Figs. 5(b'), 5(c'), 5(d'), 5(h'), and 5(i')] have similar structures as observed in the isotropic limit. Anisotropic features are less marked than in the spectral function because Eq. (14) used to determine these features does not retain information about the spectral weight in the branches.

The spectral function in the superconducting phase is gapped, and the multigap features can be clearly seen in the lower panels of Figs. 5(b*), 5(c*), 5(f*), and 5(g*). The gap ranges from 1.5 meV around the point b in the band structure [Fig. 5(b*)] to about 2.2 meV around point c [Fig. 5(c*)]. The spectral function shows a (textbooklike) hyperbolic dispersion: this is the signature of Bogoljubov excitations¹¹ as compared to the normal electronic excitations which have a linear band dispersion [see Figs. 5(c*) and 5(c#)]. The distance between the vertices of the hyperbola is equal to $2\Delta(0)$. As the temperature rises to approach T_c , $\Delta(0) \rightarrow 0$ and the hyperbola tends to its asymptotes. At the same time, the spectral weight of the two reflected components [right part of the upper branch and left part of the lower branch in Fig. 5(c*)] also goes to zero and the excitation spectrum becomes normal [Fig. 5(c#)].

One of the two arms of this hyperbolic dispersion corresponds to the normal electronic dispersion line, and it behaves in a similar way as in the nonsuperconducting state. The other arm that is a unique feature of the Bogoljubov excitations loses spectral weight as the distance from the FS increases. However, as it reaches the energy of the Ca in-plane modes (from 10 to 15 meV), it deviates from the hyperbolic arm and follows a polaronic (dispersionless) behavior. One can appreciate the formation of this dispersionless Bogoljubov polaron in the upper-right and lower-left corners of panel (b*) in Fig. 5.

V. CONCLUSIONS

Superconductivity in the graphite intercalated compound CaC_6 is studied using Eliashberg theory and superconducting density functional theory. Within a multiband description and assuming a structureless Coulomb interaction, we performed a detailed analysis of the influence of strongly anisotropic electron-phonon coupling on the \mathbf{k} dependence of the superconducting gap. Anisotropies computed with Eliashberg theory and superconducting density functional theory were found to be in very good agreement with each other and with experiments.⁴¹

In this context, from the solution of the Eliashberg equations, we have shown how anisotropic polaronic bands emerge over different Fermi-surface sheets. The interplay between superconducting (Bogoljubov) excitations and polarons has also been studied. We reported how Engelsberg-Schrieffer polarons evolve from the normal state to the superconducting state in CaC_6 .

ACKNOWLEDGMENTS

A.S. acknowledges useful discussions with A. Eiguren. S.P. acknowledges support through DOE Grant No. DE-FG02-05ER46203. S.M. acknowledges support by the Italian MIUR through Grant No. PRIN2008XWLWF9.

¹S. Engelsberg and J. R. Schrieffer, *Phys. Rev.* **131**, 993 (1963).

²G. M. Eliashberg, *Sov. Phys.-JETP* **11**, 696 (1960) [*J. Exptl. Theoret. Phys. (U.S.S.R.)* **38**, 966 (1960)].

³D. J. Scalapino, J. R. Schrieffer, and J. W. Wilkins, *Phys. Rev.* **148**, 263 (1966).

⁴A. Eiguren, S. de Gironcoli, E. V. Chulkov, P. M. Echenique, and E. Tosatti, *Phys. Rev. Lett.* **91**, 166803 (2003).

⁵A. Eiguren and C. Ambrosch-Draxl, *Phys. Rev. Lett.* **101**, 036402 (2008).

⁶D. J. Scalapino, in *Superconductivity*, edited by R. D. Parks (Marcel Dekker, New York, 1969), Vol. 1, Chap. 10, p. 449.

⁷A. W. Sandvik, D. J. Scalapino, and N. E. Bickers, *Phys. Rev. B* **69**, 094523 (2004).

⁸T. P. Devereaux, A. Virosztek, and A. Zawadowski, *Phys. Rev. B* **59**, 14618 (1999).

⁹X. J. Zhou, in *Handbook of High-Temperature Superconductivity*, edited by J. R. Schrieffer and J. S. Brooks (Springer, New York, 2007), Chap. 3.

¹⁰P. B. Allen and B. Mitrovic, in *Solid State Physics*, edited by F. Seitz (Academic, New York, 1982), Vol. 37, p. 1.

¹¹J. R. Schrieffer, *Theory of Superconductivity*, *Frontiers in Physics*, Vol. 20 (Addison-Wesley, Reading, 1964).

¹²M. S. Dresselhaus and G. Dresselhaus, *Adv. Phys.* **51**, 1 (2002).

¹³D. Chung, *J. Mater. Sci.* **37**, 1475 (2002).

¹⁴N. B. Hannay, T. H. Geballe, B. T. Matthias, K. Andres, P. Schmidt, and D. MacNair, *Phys. Rev. Lett.* **14**, 225 (1965).

¹⁵T. E. Weller, M. Ellerby, S. S. Saxena, R. P. Smith, and T. N. Skipper, *Nat. Phys.* **1**, 39 (2005).

¹⁶N. Emery, C. Hérold, M. d'Astuto, V. Garcia, Ch. Bellin, J. F. Maréché, P. Lagrange, and G. Loupias, *Phys. Rev. Lett.* **95**, 087003 (2005).

¹⁷G. Csanyi, P. B. Littlewood, A. H. Nevidomskyy, C. J. Pickard, and B. D. Simons, *Nat. Phys.* **1**, 42 (2005).

¹⁸M. Calandra and F. Mauri, *Phys. Rev. Lett.* **95**, 237002 (2005).

¹⁹I. I. Mazin, *Phys. Rev. Lett.* **95**, 227001 (2005).

²⁰L. Boeri, G. B. Bachelet, M. Giantomassi, and O. K. Andersen, *Phys. Rev. B* **76**, 064510 (2007).

²¹J. S. Kim, L. Boeri, J. R. O'Brien, F. S. Razavi, and R. K. Kremer, *Phys. Rev. Lett.* **99**, 027001 (2007).

²²I. I. Mazin, L. Boeri, O. V. Dolgov, A. A. Golubov, G. B. Bachelet, M. Giantomassi, and O. K. Andersen, *Phys. C (Amsterdam)* **460**, 116 (2007).

²³M. Calandra and F. Mauri, *Phys. Rev. B* **74**, 094507 (2006).

²⁴A. Sanna, G. Profeta, A. Floris, A. Marini, E. K. U. Gross, and S. Massidda, *Phys. Rev. B* **75**, 020511(R) (2007).

²⁵S. Baroni, S. de Gironcoli, and A. Dal Corso, *Rev. Mod. Phys.* **73**, 56 (2001).

²⁶A. Marini, G. Onida, and R. Del Sole, *Phys. Rev. Lett.* **88**, 016403 (2001).

²⁷P. Morel and P. W. Anderson, *Phys. Rev.* **125**, 1263 (1962).

²⁸C. R. Leavens and E. W. Fenton, *Solid State Commun.* **33**, 597 (1979).

²⁹C.-Y. Moon, Y.-H. Kim, and K. J. Chang, *Phys. Rev. B* **70**, 104522 (2004).

³⁰S. Massidda, F. Bernardini, C. Bersier, A. Continenza, P. Cudazzo, A. Floris, H. Glave, M. Monni, S. Pittalis, G. Profeta, A. Sanna, S. Sharma, and E. K. U. Gross, *Supercond. Sci. Technol.* **22**, 034006 (2009).

³¹J. P. Carbotte, *Rev. Mod. Phys.* **62**, 1027 (1990).

³²H. J. Vidberg and J. W. Serene, *J. Low Temp. Phys.* **29**, 179 (1977).

- ³³G. A. Baker Jr., *Essentials of Padé Approximants* (Academic, New York, 1975).
- ³⁴C. M. Bender and S. A. Orszag, *Advanced Mathematical Methods for Scientists and Engineers* (Springer, Berlin, 1999).
- ³⁵ESPRESSO package: <http://www.pwscf.org/>.
- ³⁶P. Giannozzi *et al.*, *J. Phys.: Condens. Matter* **21**, 395502 (2009).
- ³⁷J. P. Perdew and Y. Wang, *Phys. Rev. B* **45**, 13244 (1992).
- ³⁸D. Vanderbilt, *Phys. Rev. B* **41**, 7892 (1990).
- ³⁹Padé approximants were used to continue solutions of the Eliashberg equations to the real axis. Very good agreement is observed in the full energy spectrum for the $Z(\omega)$ function. Although the analytically continued gap function $\Delta(\omega)$ shows some deviations from the exact solutions, this happens in the ~ 0.1 -eV energy region (Ref. 32). As a result, this does not introduce sizable errors in our estimation of the spectral function.
- ⁴⁰D. Daghero and R. S. Gonnelli, *Supercond. Sci. Technol.* **23**, 043001 (2010).
- ⁴¹R. S. Gonnelli, D. Daghero, D. Delaude, M. Tortello, G. A. Ummarino, V. A. Stepanov, J. S. Kim, R. K. Kremer, A. Sanna, G. Profeta, and S. Massidda, *Phys. Rev. Lett.* **100**, 207004 (2008).
- ⁴²U. Nagel, D. Hüvonen, E. Joon, J. S. Kim, R. K. Kremer, and T. Rößler, *Phys. Rev. B* **78**, 041404 (2008).
- ⁴³T. Shiroka, G. Lamura, R. De Renzi, M. Belli, N. Emery, H. Rida, S. Cahen, J.-F. Marêché, P. Lagrange, and C. Hérold, *New J. Phys.* **13**, 013038 (2011).
- ⁴⁴C. Kurter, L. Ozyuzer, D. Mazur, J. F. Zasadzinski, D. Rosenmann, H. Claus, D. G. Hinks, and K. E. Gray, *Phys. Rev. B* **76**, 220502(R) (2007).
- ⁴⁵A. Floris, G. Profeta, N. N. Lathiotakis, M. Lüders, M. A. L. Marques, C. Franchini, E. K. U. Gross, A. Continenza, and S. Massidda, *Phys. Rev. Lett.* **94**, 037004 (2005).
- ⁴⁶A. Floris, A. Sanna, M. Lüders, G. Profeta, N. N. Lathiotakis, M. A. L. Marques, E. K. U. Gross, A. Continenza, and S. Massidda, *Phys. C (Amsterdam)* **456**, 45 (2007).